

承认书

APPROVAL SHEET

产品名称： 多层片式陶瓷电容器

PART NAME: MULTILAYER CERAMIC CAPACITORS

系 列： 安全规格系列（AC 250V）

SERIES： Safety Specification Series（AC 250V）

尺寸规格： 1808 ~ 2220

Size: 1808 ~ 2220

供 应 商（SUPPLIER）： 利和兴电子元件(江门)有限公司

发布日期（ISSUED DATE）：

批 准（APPROVED BY）：

一、MLCC 简介 General Introduction	2
二、MLCC 介质种类 MLCC Dielectric Types	2
三、MLCC 产品尺寸与结构 Product Size and Structure	3
四、产品规格表示方法 Part Number Structure	4
② 尺寸规格 Size Specification(mm)	4
③ 介质种类 Dielectric Type	4
④ 静电容量 Capacitance	4
⑤ 静容量公差 Capacitance Tolerance	5
⑥ 额定电压 Rated Voltage	5
⑦ 类型 Type	5
五、温度系数/特性 Temperature Coefficient /Characteristics	5
六、产品范围、尺寸、厚度 Product Range、Size & Thickness	6
七、可靠性测试方法 Reliability Test Methods	7
八、包装 Package	11
① 产品厚度和包装数量 Thickness and Packing Amount	11
② 带式圆盘包装 Tape and Reel Package	11
③ 纸带卷盘结构 Paper Taping	12
④ 纸带标准 Paper Tape Specifications	12
⑤ 塑胶卷盘结构 Embossed Taping	13
⑥ 传送带的前后结构 Front end and Back end Structure of Carrier Tape	14
⑦ 纸带性能 Performance of Taping	15
⑧ 纸带和上盖带的剥离性能 Peeling Force of Carrier Tape and Top Cover Tape	15
⑨ 外箱包装 Outer packing	16
九、储存方法 Storage Methods	16
十、使用前的注意事项 PreEutions For Use	16
① 焊接的条件与相关图表 Soldering Profile	16
② 手工焊接 Manual Soldering	17
③ 适量的焊料 Optimum Solder Amount for Reflow Soldering	17
④ 推荐焊料用量 Recommended Soldering amounts	17
十一、推荐焊接温度曲线图 The temperature profile for soldering	18

一、MLCC 简介

片式多层陶瓷电容器 (MLCC) 是适合于表面贴装技术 (SMT) 的小尺寸、高比容、高精度陶瓷介质电容器, 可贴装于印刷线路板 (PCB)、混合集成电路 (HIC) 基片, 有效地缩小电子信息终端产品 (尤其是便携式产品) 的体积和重量, 提高产品可靠性。顺应了 IT 产业小型化、轻量化、高性能、多功能的发展方向, 陶瓷电容器适合厂家高密度、高效表面贴装。

General Introduction

Multi-layer ceramic chip capacitor is a kind of ceramic dielectric capacitor with small size, high capacitance per volume, high accuracy, suited surface mounted technology (SMT). It is widely used in electronic circuitry, mounted printed circuit board, and hybrid IC. These different functions require specific capacitor properties.

二、MLCC 介质种类

产品采用的介质材料可以分为两大类:

I类陶瓷介质电容器, 称为高频电容器, 包括通用型高频 COG、COH 电容器和温度补偿型高频 HG、LG、PH、RH、SH、TH、UJ、SL 电容器。高频电容器具有极高的稳定性, 其中 COG、COH 电容器电性能几乎不随时间、交流信号、外加直流偏压的变化而改变, 同时具有极低介质损耗, 即高 Q 值。适用于低损耗、温度补偿型电路中。

II类陶瓷介质陶瓷电容器, 包括 X5R、X6S、X7R、X7S、X7T 介质材料的电容器为II类电容器, 具有较高的介电常数, 容量比I类电容器高, 具有较稳定的温度特性, 更宽的容量范围, 一般电路中, 如隔直、耦合、旁路、鉴频等电路中。

MLCC Dielectric Types

The dielectric materials used in the products can be divided into two broad categories:

Class I dielectric ceramic capacitors, called high-frequency capacitors, including Standard high-frequency COG, COH capacitors and temperature-compensated high-frequency HG, LG, PH, RH, SH, TH, UJ, SL capacitors. High-frequency capacitors have a very high stability, where COG, COH capacitor electrical performance almost does not change over time, AC signal, plus DC bias, while having very low dielectric loss, that is, high Q value. Suitable for low-loss, temperature-compensated circuits.

Class II dielectric ceramic capacitors, including X5R, X6S, X7R, X7S, X7T dielectric material, Class II dielectric capacitors, with a higher dielectric constant, higher capacitance than Class I capacitors, with stable temperature characteristics, with a wider range of capacitance, In general circuit, such as DC blocking, coupling, bypass, frequency discriminator and other circuits.

三、MLCC 产品尺寸与结构
Product Size and Structure


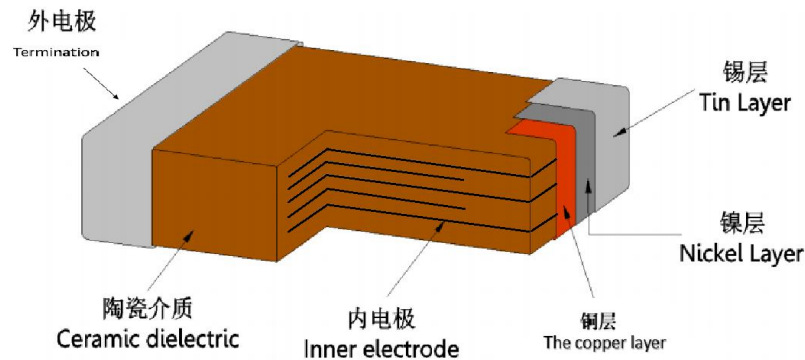


图 1 片式多层陶瓷电容器外形与内部结构
Figure 1 Dimension and Cross-section of MLCC

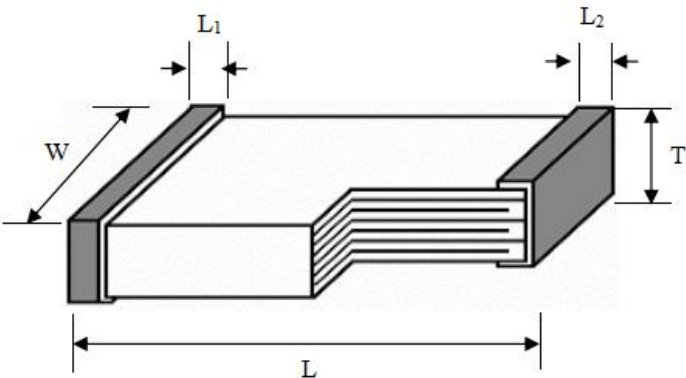

尺寸代码 Size Code (EIA)	L	W	L ₁ /L ₂	T	厚度代码 Thickness Code
1808	4.50±0.40	2.00±0.20	≤0.7	1.60±0.30	P
				2.00±0.30	U
1812	4.50±0.40	3.20±0.20	≤0.7	1.60±0.30	P
				2.00±0.30	U
2211	5.70±0.40	2.80±0.30	≤1.0	1.60±0.30	P
				2.00±0.30	U
				2.50±0.30	V
2220	5.70±0.40	5.00±0.40	≤1.0	1.60±0.30	P
				2.00±0.30	U

四、产品规格表示方法

Part Number Structure

LCU	1812	X7R	681	K	302	X1
①	②	③	④	⑤	⑥	⑦

① 产品系列 Series

代码 Code	表示名称 Name
L	利和兴 Lihexing
C	电容器 Capacitor
U	安全规格系列 Safety Specification Series

② 尺寸规格 Size Specification(mm)

英制表示 BRITISH	长×宽 (L×W) INCH	长×宽 (L×W) MM
1808	0.18×0.08	4.50×2.00
1812	0.18×0.12	4.50×3.20
2211	0.22×0.11	5.70×2.80
2220	0.22×0.20	5.70×5.00

③ 介质种类 Dielectric Type

I类陶瓷介质 Class I Ceramic Dielectrics	II类陶瓷介质 Class II Ceramic Dielectrics
C0G	X7R

④ 静电容量 Capacitance

代码 Code	表示值 Indicated value	静电容量 Capacitance	说明 Explanation
0R5	0.5	0.5pF	静电容量由3位字符表示。单位为皮法(pF)。第1位和第2位数字为有效数字,第3位数字表示有效数字后的0的个数。有小数点时以大写字母"R"表示。此时,所有数字均为有效数字。如果包含有任何不是"R"的字母,则表明该特指的品名是一个非标准的部件。 Nominal capacitance is represented by 3 digits, with the unit of picofarad (pF). The first and second digits are significant digits, and the third digit identifies the multiplier. When there is a decimal point, it is represented by a capital letter "R". At this time, all numbers are valid numbers. If it contains any letter other than "R", it indicates that the specified product name is a non-standard part.
1R0	1.0	1.0pF	
100	10	10pF	
102	10×10 ²	1000pF	
104	10×10 ⁴	100000pF	
...	...	...	

⑤ 静容量公差 Capacitance Tolerance

代码 Code	静容量公差 Capacitance Tolerance	说明 Explanation
B	$\pm 0.10\text{pF}$	B、C、D 级误差适用于容量 $\leq 10\text{pF}$ 的产品 B, C, D level error is applicable to products with capacitance $\leq 10\text{pF}$
C	$\pm 0.25\text{pF}$	
D	$\pm 0.5\text{pF}$	
F	$\pm 1.0\%$	
G	$\pm 2.0\%$	
J	$\pm 5.0\%$	
K	$\pm 10\%$	
M	$\pm 20\%$	

⑥ 额定电压 Rated Voltage

代码 Code	表示值 Indicated value
302	交流 250V AC 250V

⑦ 类型 Type

类型代码 Type code	使用时的峰值脉冲电压 Peak pulse Voltage in use
X1	4KV
X2	2.5KV
Y2	5KV

五、温度系数/特性

Temperature Coefficient /Characteristics

介质种类 Dielectric	参考温度点 Reference Temperature Point	标称温度系数 Temperature Coefficient	工作温度范围 Operation Temperature Range
C0G	20°C	0 $\pm$ 30 ppm/°C	-55°C ~ +125°C
X7R	20°C	$\pm 15\%$	-55°C ~ +125°C

备注：I类介质电容器标称温度系数和允许偏差是采用温度在 20°C 和 85°C 之间的电容量变化来确定的。

Note: Nominal temperature coefficient and allowed tolerance of class I are decided by the changing of the capacitance between 20°C and 85°C.

六、产品范围、尺寸、厚度


Product Range、Size & Thickness


尺寸代码 Size Code	类型 Type	标称电容量范围 Nominal Capacitance Range		厚度代码 Thickness Code
		C0G	X7R	
1808	X1	—	101-102	P
	X1	—	122-222	U
	X2	—	101-472	P
	X2	—	—	—
	Y2	5R6-121	101-102	P
	Y2	151-331	122-222	U
1812	X2	—	101-103	P
	X2	—	—	—
	Y2	5R6-121	101-152	P
	Y2	151-331	182-472	U
2211	Y2	5R6-221	101-222	P
	Y2	—	272-332	U
2220	X2	—	101-103	P
	X2	—	123-153	U
	Y2	5R6-271	101-182	P
	Y2	331-471	272-472	U


七、可靠性测试方法

Reliability Test Methods

项目 Item	技术要求 Technical Requirements	测试方法 Test Method and Remarks								
容量 Capacitance	应符合指定的误差级别 Should be within the specified tolerance	C0G:								
损耗角正切 (DF, tan δ) Dissipation Factor	C0G: C<30pF, DF≤1/(400+20C); C≥30 pF, DF≤0.1% X7R: DF≤2.5%	标称容量 Capacitance	测试频率 Measuring Frequency	测试电压 Measuring Voltage						
		≤1000pF	1MHz ±10%	1.0±0.2Vrms						
		>1000 pF	1KHz ±10%	1.0±0.2Vrms						
		X7R:								
		标称容量 Capacitance	测试频率 Measuring Frequency	测试电压 Measuring Voltage						
		≤10μF	1KHz ±10%	1.0±0.2Vrms						
		>10μF	120+/-24Hz	0.5±0.1Vrms						
绝缘电阻(IR) Insulation Resistance	C0G: C≤10 nF, Ri≥50000MΩ; C>10 nF, Ri•CR≥500s; X7R: C≤25 nF, Ri≥10000MΩ; C>25 nF, Ri•CR≥100s	测试电压: UR≤500V, 额定电压; UR>500V, 500V 测试时间: 60±5 秒 测试湿度: ≤75% 测试温度: 25°C±3°C 测试充放电电流: ≤50mA Measuring Voltage: UR≤500V, Rated Voltage; UR>500V, 500V; Duration: 60±5s Test Humidity: ≤75% Test Temperature: 25°C±3°C Test Current: ≤50mA								
介质耐电强度(DWV) Dielectric Withstanding Voltage	不应有介质被击穿或损伤 No breakdown or damage	在端子间施加表中的电压 60±1S 时不应观察到任何故障, 并且充电/放电电流不超过 50mA。 No failure should be observed when Voltage in the table is applied between the terminations for 60 sec.provided the charge/discharge current is less than 50mA.								
		<table><tr><td colspan="2">测试电压 Test Voltage</td></tr><tr><td>X1、X2</td><td>DC 1075V</td></tr><tr><td>Y2</td><td>AC 1500V</td></tr></table>			测试电压 Test Voltage		X1、X2	DC 1075V	Y2	AC 1500V
测试电压 Test Voltage										
X1、X2	DC 1075V									
Y2	AC 1500V									

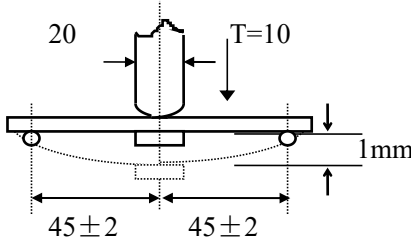项目 Item	技术要求 Technical Requirements		测试方法 Test Method and Remarks												
可焊性 Solderability	上锡率应大于 95% 外观无可见损伤。 At least 95% of the terminal electrode is covered by new solder。 Visual Appearance： No visible damage。		将电容在 80~120℃ 的温度下预热 10~30 秒。 Preheating Conditions:80 to 120℃； 10~30s。 无铅焊料： (Lead Free) 浸锡温度： 245±5℃ 浸锡时间： 2±0.5s Solder Temperature: 245±5℃ Duration: 2±0.5s												
耐焊接热 Resistance to Soldering Heat	<table><tr><td>项目 Item</td><td>C0G</td><td>X7R</td></tr><tr><td>△C/C</td><td>≤ ±2.5%或±0.25pF， 取较大者 whichever is larger.</td><td>≤±15%</td></tr><tr><td>Q 或 DF</td><td colspan="2">同初始标准 Same to initial value.</td></tr><tr><td>IR (25℃)</td><td colspan="2">同初始标准 Same to initial value.</td></tr></table> 外观： 无可见损伤 Appearance： No visible damage	项目 Item	C0G	X7R	△C/C	≤ ±2.5%或±0.25pF， 取较大者 whichever is larger.	≤±15%	Q 或 DF	同初始标准 Same to initial value.		IR (25℃)	同初始标准 Same to initial value.		将电容在 100~200℃ 的温度下预热 60~120 秒。 浸锡温度： 265±5℃ 浸锡时间： 10±1s 然后取出溶剂清洗干净，在 10 倍以上的显微镜底下观察。 放置时间： 24±2 小时，放置条件： 室温 Preheating Conditions:100 to 200℃; 60~120s. Solder Temperature:265±5℃ Duration:10±1s Clean the capacitor with solvent and examine it with a 10X(min.) microscope。 Recovery Time:24±2h Recovery Condition:Room temperature	
项目 Item	C0G	X7R													
△C/C	≤ ±2.5%或±0.25pF， 取较大者 whichever is larger.	≤±15%													
Q 或 DF	同初始标准 Same to initial value.														
IR (25℃)	同初始标准 Same to initial value.														
脉冲电压 Impulse Voltage	无永久性击穿或飞弧。 No permanent break down or flashover.		每个电容器应承受 24 次相同极性的脉冲，脉冲间隔时间不应小于 10S，脉冲电压峰值如下表： Each capacitor shall withstand 24 pulses of the same polarity, the pulse interval time shall not be less than 10S, and the peak value of pulse Voltage like the follow table： <table><tr><td>类型 Code</td><td>使用时的峰值脉冲电压(kV) Peak pulse Voltage in use (kV)</td></tr><tr><td>X1</td><td>4.0</td></tr><tr><td>X2</td><td>2.5</td></tr><tr><td>Y2</td><td>5.0</td></tr></table>	类型 Code	使用时的峰值脉冲电压(kV) Peak pulse Voltage in use (kV)	X1	4.0	X2	2.5	Y2	5.0				
类型 Code	使用时的峰值脉冲电压(kV) Peak pulse Voltage in use (kV)														
X1	4.0														
X2	2.5														
Y2	5.0														
抗弯曲强度 Bending Strength	<table><tr><td>项目 Item</td><td>C0G</td><td>X7R、X5R、X7S、X6S</td></tr><tr><td>△C/C</td><td>≤ ±5%或±0.5pF， 取较大者 whichever is larger.</td><td>≤±10%</td></tr></table> 外观： 无可见损伤 Appearance： No visible damage	项目 Item	C0G	X7R、X5R、X7S、X6S	△C/C	≤ ±5%或±0.5pF， 取较大者 whichever is larger.	≤±10%	试验基板： PCB； 弯曲深度： 1mm 施压速度： 1mm/sec； 保持时间： 5s 应在弯曲状态下进行测量。  Test Board: PCB Warp: 1mm Speed: 1mm/sec. Hold time: 5 sec The measurement should be made with the board in the bending position.							
项目 Item	C0G	X7R、X5R、X7S、X6S													
△C/C	≤ ±5%或±0.5pF， 取较大者 whichever is larger.	≤±10%													

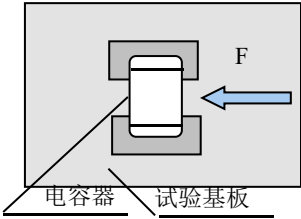项目 Item	技术要求 Technical Requirements	测试方法 Test Method and Remarks												
端头结合强度 Termination Adhesion	外观: 无可见损伤 Appearance: No visible damage	将产品焊在试验板上, 施加推力 F Solder the product onto the test board and apply a thrust force F. <table border="1"> <thead> <tr> <th>规格 Specification</th><th>施加力 F Apply force F</th><th>时间 Time (S)</th></tr> </thead> <tbody> <tr> <td>≤0402</td><td>2N</td><td>10±1</td></tr> <tr> <td>≥0603</td><td>5N</td><td>10±1</td></tr> </tbody> </table>  电容器 试验基板	规格 Specification	施加力 F Apply force F	时间 Time (S)	≤0402	2N	10±1	≥0603	5N	10±1			
规格 Specification	施加力 F Apply force F	时间 Time (S)												
≤0402	2N	10±1												
≥0603	5N	10±1												
温度循环 Temperature Cycle	<table border="1"> <thead> <tr> <th>项目 Item</th><th>C0G</th><th>X7R</th></tr> </thead> <tbody> <tr> <td>ΔC/C</td><td>≤ ±1%或±1pF, 取较大者 whichever is larger.</td><td>≤±15%</td></tr> </tbody> </table> 外观: 无可见损伤 Appearance: No visible damage	项目 Item	C0G	X7R	ΔC/C	≤ ±1%或±1pF, 取较大者 whichever is larger.	≤±15%	循环次数: 5 次, 一个循环分以下 4 步: 阶段 1: 下限温度 -55℃; 时间 30 分钟; 阶段 2: 常温 20℃; 时间 1 分钟; 阶段 3: 上限温度; 时间 30 分钟; 阶段 4: 常温 20℃; 时间 1 分钟。 Cycling Times: 5times. A cycle is divided into the following 4 steps: Step1: Lower limit temperature :-55℃; 30 minutes; Step2: Normal temperature :20℃; 1 minutes; Step3: Upper limit temperature; 30 minutes; Step4: Normal temperature :20℃; 1 minute.						
项目 Item	C0G	X7R												
ΔC/C	≤ ±1%或±1pF, 取较大者 whichever is larger.	≤±15%												
潮湿负荷 Humidity load	<table border="1"> <thead> <tr> <th>项目 Item</th><th>C0G</th><th>X7R</th></tr> </thead> <tbody> <tr> <td>ΔC/C</td><td>≤ ±7.5%或±0.75pF, 取较大者。 whichever is larger.</td><td>≤±12.5%</td></tr> <tr> <td>Q 或 DF</td><td colspan="2">≤2 倍初始标准 Not more than twice of initial value.</td></tr> <tr> <td>IR (25℃)</td><td colspan="2">≥0.1 倍初始标准 Not less than 0.1 times the initial standard.</td></tr> </tbody> </table> 外观: 无可见损伤 Appearance: No visible damage	项目 Item	C0G	X7R	ΔC/C	≤ ±7.5%或±0.75pF, 取较大者。 whichever is larger.	≤±12.5%	Q 或 DF	≤2 倍初始标准 Not more than twice of initial value.		IR (25℃)	≥0.1 倍初始标准 Not less than 0.1 times the initial standard.		温度: 40±2℃ 湿度: 90~95%RH 电压: 额定电压 时间: 500 小时 放置条件: 室温 放置时间: 24±2 小时。 Temperature: 40±2℃ Humidity: 90~95%RH Voltage: Rated Voltage Duration: 500h Recovery Conditions: Room temperature Recovery Time: 24±2h .
项目 Item	C0G	X7R												
ΔC/C	≤ ±7.5%或±0.75pF, 取较大者。 whichever is larger.	≤±12.5%												
Q 或 DF	≤2 倍初始标准 Not more than twice of initial value.													
IR (25℃)	≥0.1 倍初始标准 Not less than 0.1 times the initial standard.													

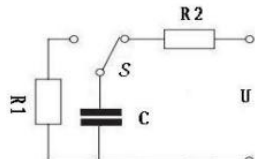项目 Item	技术要求 Technical Requirements			测试方法 Test Method and Remarks		
充放电 Charge and discharge						
				如下图所示安放 被测器件 C, 承受 10000 次充放电循环: 充电电压: 额定电压 充放电电流: ≤1A As shown in the following figure, the device under test C is placed and subjected to 10000 charge and discharge cycles. Charge Voltage: Ur Charge and discharge current: ≤1A		
	项目 Item	C0G	X7R	代码 Code	参数 Parameter	
	ΔC/C	≤ ±2%或±0.2pF, 取较大者。 whichever is larger.	≤±10%	C	样品电容 Sample capacitance	
	Q 或 DF	同初始标准 Same to initial value.			R1	放电限流电阻 Current-limiting resistor (discharge)
	IR (25°C)	Ri≥2500MΩ或 Ri•C≥25S 取两者之中较小者 whichever is smaller	Ri≥1000MΩ或 Ri•C≥10S 取两者之中较小者 whichever is smaller	R2	充电限流电阻 Current-limiting resistor (charge)	
外观: 无可见损伤 Appearance: No visible damage			U	充电电压 Charge Voltage		
			S	开关器件 Switching device		
寿命试验 Life Test	项目 Item	C0G	X7R	脉冲电压试验完成后的一周内进行. 温度: 125°C(C0G/X7R)时间: 1000 小时 充电电流: 不应超过 50mA 施加电压: X1/X2: 1.25*UR; Y2: 1.7*UR 电容器串联一个 47Ω±5%电阻器; 每小时一次将电压升高至 1000V, 持续时间 0.1s。 放置条件: 室温, 放置时间: 24±2 小时 This test shall be conducted within one week after the completion of impulse Voltage test. Temperature: 125°C (C0G/X7R) Duration: 1000h Charge/ Discharge Current: 50mA max. Applied Voltage: X1/X2: 1.25*UR; Y2: 1.7*UR The capacitor is connected in series with a 47 Ω±5%resistor. Raise the Voltage to 1000V once an hour for 0.1sec.		
	ΔC/C	≤ ±3%或±0.3pF, 取较大者 whichever is larger.	≤±20%			
	Q 或 DF	≤2 倍初始标准 Not more than twice of initial value.				
	IR (25°C)	Ri≥4000MΩ或 Ri•CR≥40S 取两者之中较小者。 whichever is smaller.	Ri≥2000MΩ或 Ri•CR≥50S 取两者之中较小者。 whichever is smaller.			
	外观: 无可见损伤 Appearance: No visible damage					

*预处理 (仅针对II类电容器): 在 $140^\circ\text{C} \sim 150^\circ\text{C}$ 下预热 $1\text{h} \pm 10\text{min}$ 后, 在室温下放置 $24 \pm 2\text{h}$ 。

实验结束后处理 (仅针对II类电容器): 在 $140^\circ\text{C} \sim 150^\circ\text{C}$ 下预热 $1\text{h} \pm 10\text{min}$ 后, 在室温下放置 $24 \pm 2\text{h}$ 。

*Pre-conditioning (for Class II capacitors only): Preheat at 140°C to 150°C for 1 hour ± 10 minutes, then store at room temperature for 24 ± 2 hours.

Post-test treatment (for Class II capacitors only): Preheat at 140°C to 150°C for 1 hour ± 10 minutes, then store at room temperature for 24 ± 2 hours.

八、包装

Package

① 产品厚度和包装数量 Thickness and Packing Amount


尺寸 Size	厚度代码 Thickness Code	纸带 7"Reel Paper Tape	胶带 7"Reel Embossed Tape
		Standard Qty(pcs)	Standard Qty(pcs)
0201	C	15000	-----
0402	E	10000	-----
0603	H	4000	-----
0805	G/H	4000	-----
	L	-----	3000
1206	G/H	4000	-----
	J/L	-----	3000
	P	-----	2000
1210	L/P	-----	2000
	U/V	-----	1000
1808/1812	L/P/U	-----	1000
	V/W	-----	500
2220	P/U/V	-----	500

② 带式圆盘包装 Tape and Reel Package

带式圆盘包装在高速 SMT 生产中广泛应用.典型的直径为 180mm(7 英寸)的圆盘可以包装 1500-15000 粒电容, 直径为 330mm(13 英寸)的圆盘可以包装 10000-50000 粒电容.带式圆盘包装包括纸带包装、胶带包装两种方式。

Tape and reel packaging is currently the most popular system for high-speed SMT production, A typical 180mm(7inch)diameter reel contains 1500 to 15,000 capacitors,330mm(13inch)diameter reel contains 10,000 to 50,000 capacitors, Tape and reel packaging comprises paper tapes and embossed tapes.


③ 纸带卷盘结构 Paper Taping

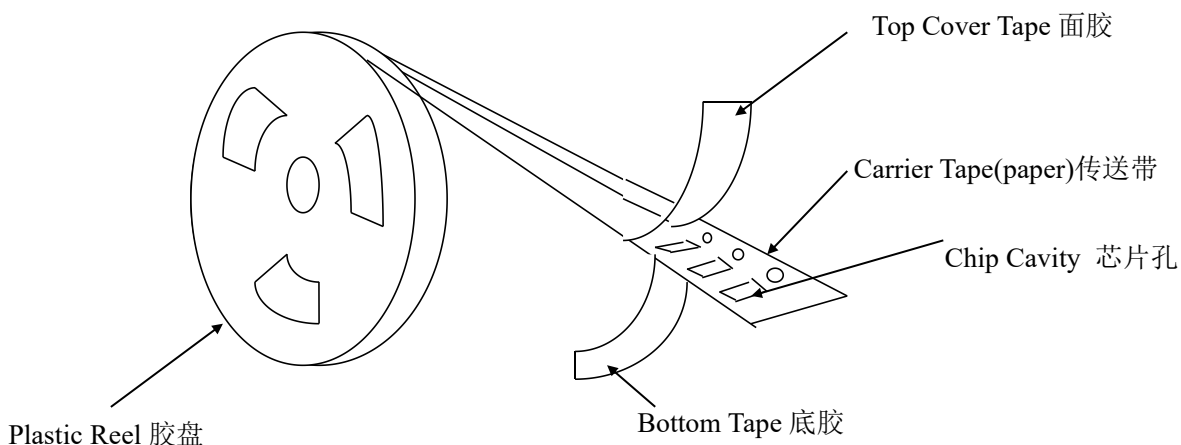

④ 纸带标准 Paper Tape Specifications

适合 0805 产品的纸带尺寸

Dimensions of paper taping for 0805 types.

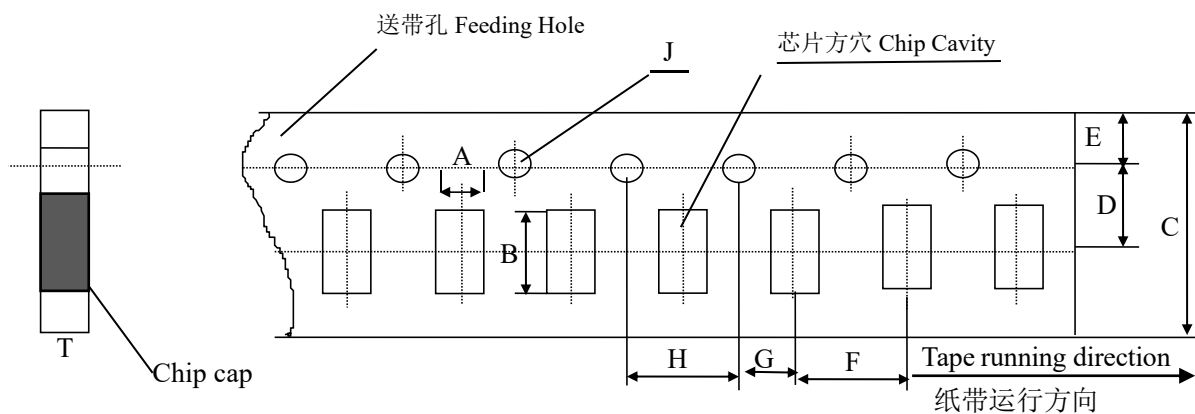


代码 Code 纸带规格 Paper size	A	B	C	D*	E	F	G*	H	J	T
0201	0.37 ±0.10	0.67 ±0.10	8.00 ±0.10	3.50 ±0.05	1.75 ±0.10	2.00 ±0.05	2.00 ±0.05	4.00 ±0.10	1.50 -0/+0.10	0.80 Below
0402	0.65 ±0.10	1.15 ±0.10	8.00 ±0.10	3.50 ±0.05	1.75 ±0.10	2.00 ±0.05	2.00 ±0.05	4.00 ±0.10	1.50 -0/+0.10	0.80 Below
0603	1.10 ±0.10	1.90 ±0.10	8.00 ±0.10	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.10	4.00 ±0.10	1.50 -0/+0.10	1.10 Max
0805	1.45 ±0.15	2.30 ±0.15	8.0 ±0.15	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.10	4.00 ±0.10	1.50 -0/+0.10	1.10 Max
1206	1.80 ±0.20	3.40 ±0.20	8.00 ±0.20	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.10	4.00 ±0.10	1.50 -0/+0.10	1.10 Max

注意：*表示此处对尺寸的要求非常精确。


Note: The place with “*” means where needs exactly dimensions

⑤ 塑胶卷盘结构 Embossed Taping

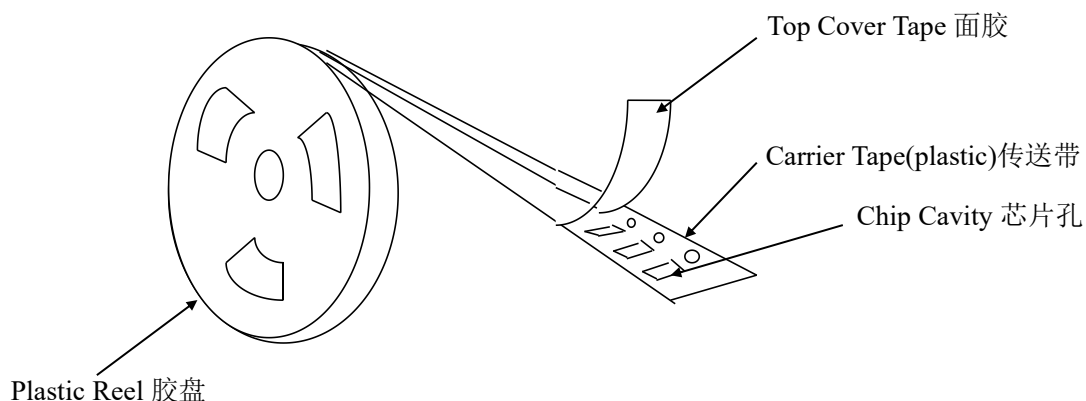

※ 塑胶带尺寸结构(适合 0805、1206、1210 型产品)

Dimensions of embossed taping for 0805, 1206, 1210type

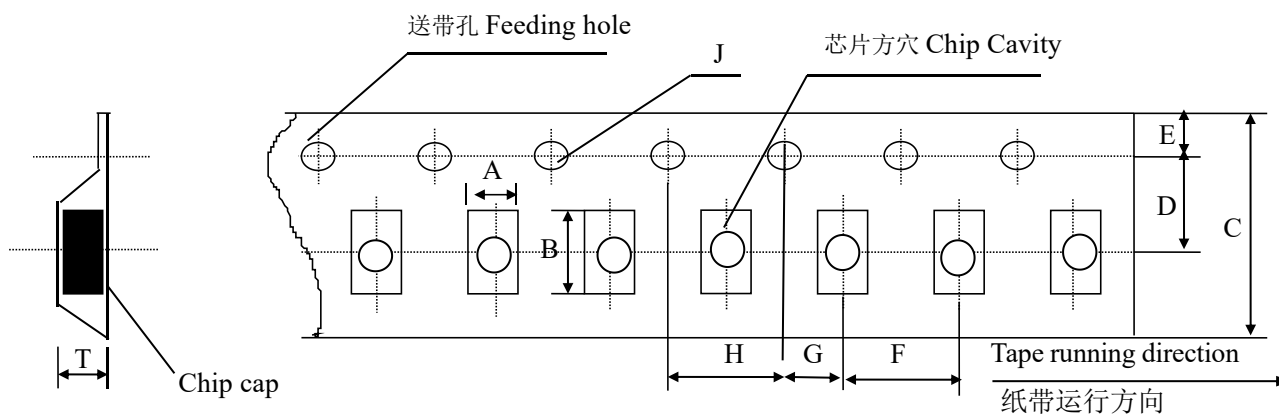


代码 Code 规格 Tape size	A	B	C	D*	E	F	G*	H	J	T
0805	1.55 ±0.20	2.35 ±0.20	8.00 ±0.20	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.10	4.00 ±0.10	1.50 -0/+0.10	1.50 Max
1206	1.95 ±0.20	3.60 ±0.20	8.00 ±0.20	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.10	4.00 ±0.1	1.50 -0/+0.10	1.85 Max
1210	2.70 ±0.10	3.42 ±0.10	8.00 ±0.10	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.05	4.00 ±0.10	1.55 -0/+0.10	3.20 Max
1808	2.70 ±0.10	3.42 ±0.10	8.00 ±0.10	3.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.05	4.00 ±0.10	1.55 -0/+0.10	3.20 Max
1812	2.20 ±0.10	4.95 ±0.10	12.00 ±0.10	5.50 ±0.05	1.75 ±0.10	4.00 ±0.10	2.00 ±0.05	4.00 ±0.10	1.50 -0/+0.10	3.00 Max


备注: *表示此处对尺寸的要求非常精确。

Note: The place with "*" means where needs exactly dimensions.

⑥ 传送带的前后结构 Front end and Back end Structure of Carrier Tape

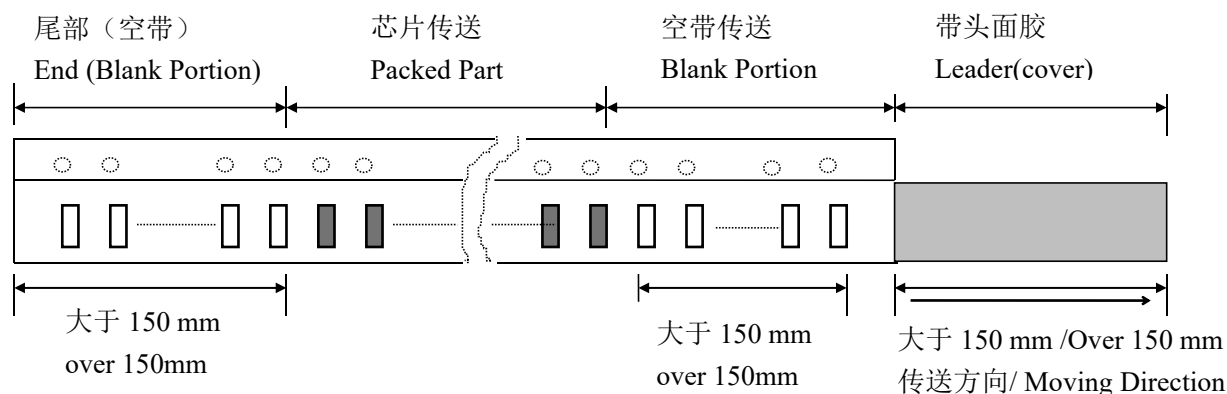

a 卷盘尺寸 Reel Dimensions(unit: mm)

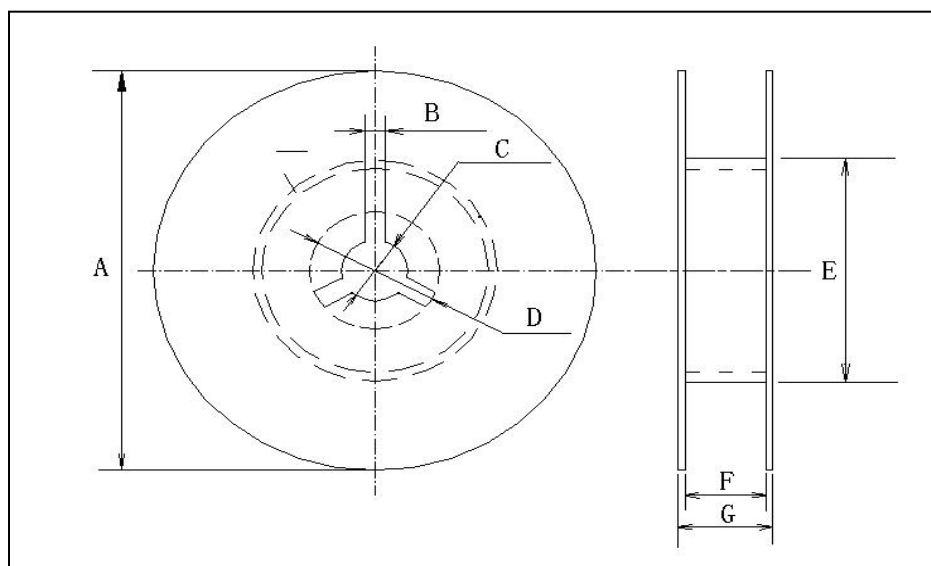

b 尺寸代码 (Size Code)

卷盘型号	A	B	C	D	E	F	G
7' Reel	$\phi 178 \pm 2.0$	3.0	$\phi 13 \pm 0.5$	$\phi 21 \pm 0.8$	$\phi 50$ 或更大 $\phi 50$ or more	10.0 ± 1.5	12max
13' Reel	$\phi 330 \pm 2.0$	3.0	$\phi 13 \pm 0.5$	$\phi 21 \pm 0.8$	$\phi 50$ 或更大 $\phi 50$ or more	10.0 ± 1.5	12max

⑦ 纸带性能 Performance of Taping

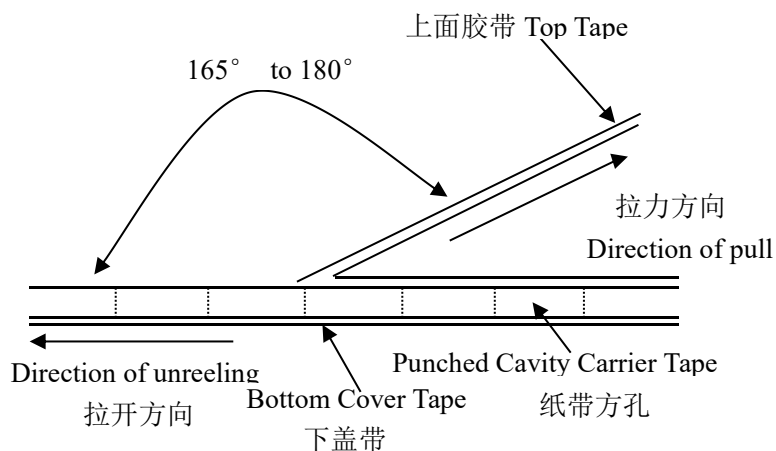


图 a

⑧ 纸带和上盖带的剥离性能 Peeling Force of Carrier Tape and Top Cover Tape

- (a) 纸带在伸直状态下应该能经受 1.02kg 的压力。

The paper tape shall be able to with stand a pressure of 1.02kg in the straight state

- (b) 上盖带应该能经受 1.02kg 的拉力。

The top cover tape should with stand 1.02kg of pull force

- (c) 上盖带剥离强度 Peeling Force of Top Cover Tape

除非有特殊规定, 上盖带以 300mm/min 的速度, 165~180°的角度 (图 a) 剥离纸带时, 剥离力度应该在 10~60g 之间。


Unless otherwise specified, the peeling force of top cover tape shall be 10g to 60g when the top cover tape is pulled at a speed of 300mm/min with the angle between the taped during peeling and the direction of unreeling maintained at 165 to 180°as shown in figure (Figure a).

⑨ 外箱包装 Outer packing

小包装 The inner package

Quantity: 10 reels


数量: 10 卷

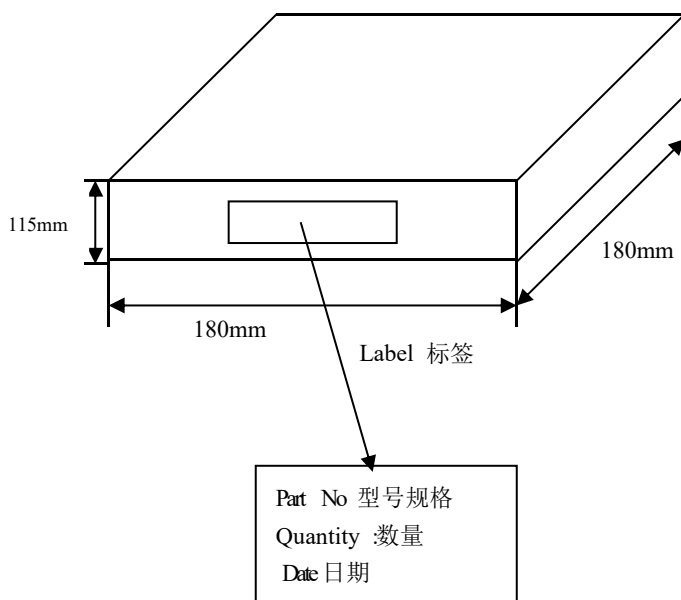

大包装 The outer package

Quantity: 6 inner boxes

数量: 6 盒

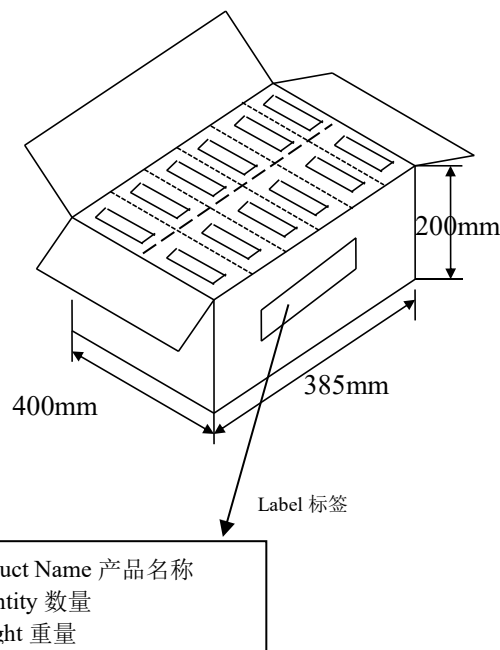

九、储存方法

Storage Methods

确保芯片可焊性良好的贮存期限为 6 个月(在包装好已交付的情况下)。

The guaranteed period for solderability is 6 months (Under deliver package condition).

储存条件/Storage Conditions:

储存温度/Storage Temperature: 5~40℃, 储存相对湿度/Relative Humidity: 20~70%

十、使用前的注意事项

Precautions For Use

多层片式瓷介电容器(MLCC)在短路或开路的电路中都有可能失效, 在超出本承认书或相关说明书中所述使用的恶劣工作环境, 或外界机械力超压作用下, 电容芯片都有可能着火、燃烧甚至爆炸, 所以在使用的時候, 首先应考虑按本承认书的有关说明来进行, 如有不明之处, 请联系厂家咨询。

The Multi-layer Ceramic Capacitors (MLCC) may fail in a short circuit or in an open circuit mode when subjected to severe conditions of electrical environment and / or mechanical stress beyond the specified “rating” and specified “conditions” in the specification, which

will result in burn out, flaming or explosion in the worst case. Following “precautions for “safety” and Application Notes shall be taken in your major consideration.

① 焊接的条件与相关图表 Soldering Profile

为避免因温度的突然变化而引起的芯片开裂或局部开裂的现象发生, 请按有关温度曲线图表来进行(请参考附页中的图表)。

To avoid the crack problem by sudden temperature change, follow the temperature profile in the related

graph (refer to the graph in the enclosure page).


② 手工焊接 Manual Soldering

手工焊接很容易因为芯片局部受热不均而引起瓷体微裂或局部开裂的现象,在焊接时,如果操作者不小心,会使烙铁头直接同电容芯片的瓷体部分接触,这样很容易使电容芯片因热冲击而受损或出现其他意外。因此,使用电烙铁手工焊接时应仔细操作,并对电烙铁的尖端的选择和尖端温度控制应多加小心。

Manual welding is easy to cause microcrack or partial cracking because of uneven heating of chip. The hot soldering iron tip comes into direct contact with the end terminations, and operator's careless may cause the tip of the soldering iron to come into direct contact with the ceramic body of the capacitor. Therefore the soldering iron must be handled carefully, and pay much attention to the selection of the soldering iron tip and temperature contact of the tip.


③ 适量的焊料 Optimum Solder Amount for Reflow Soldering

焊料过多
Too much solder

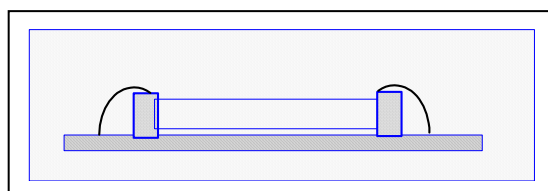

这样会因端头压力过大可能引起芯片受损
Cracks tend to occur due to large stress.

焊料太少
Not enough solder

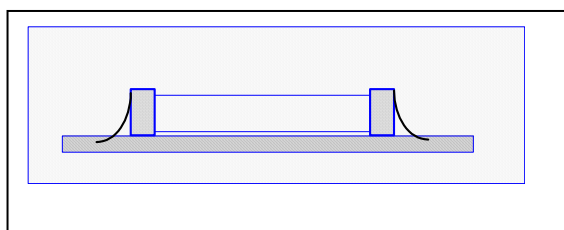


固定力量不足,可能会引起电容芯片与线路接触不良
Weak holding force may cause bad connection between the capacitor and PCB

④ 推荐焊料用量 Recommended Soldering amounts



a.回流焊接的最佳焊料用量

The optimal solder amounts for re-flow soldering

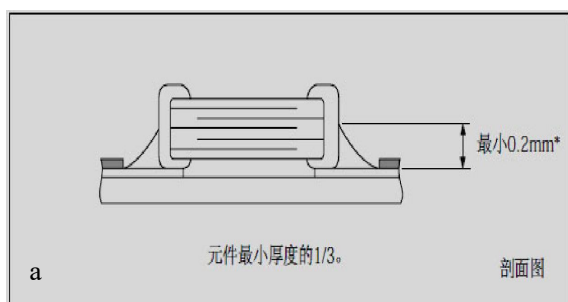

b.波峰焊接的最佳焊料用量

The optimal solder amounts for wave soldering

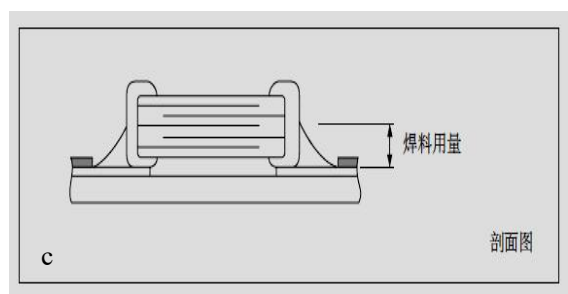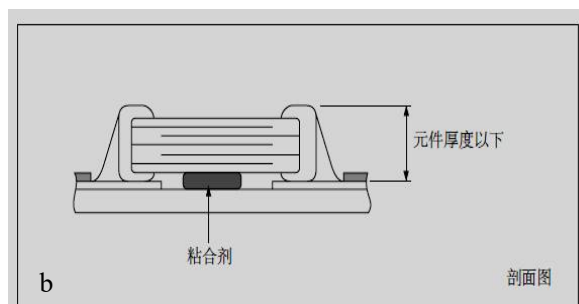


c.使用烙铁返修时的最佳焊料量

The optimal solder amounts for reworking by using soldering iron

十一、推荐焊接温度曲线图

The temperature profile for soldering

(a) 回流焊接（Re-flow soldering）

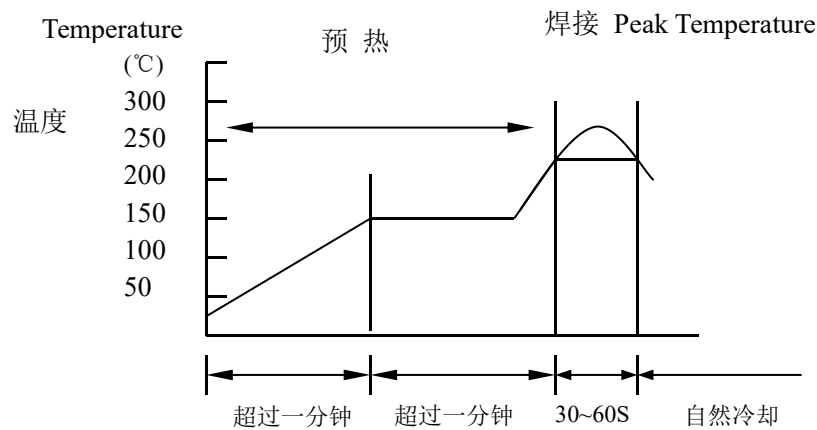


/	Pb-Sn 焊接 Pb-Sn soldering	无铅焊接 Lead-free soldering
尖峰温度 Peak temperature	230℃～250℃	240℃～260℃

在预热时，请将焊接温度与芯片表面温度之间的温差维持在 $T \leq 150^{\circ}\text{C}$ 。

While in preheating, please keep the temperature difference between soldering temperature and surface temperature of chips as: $T \leq 150^{\circ}\text{C}$.

(b) 波峰焊接（Wave soldering）

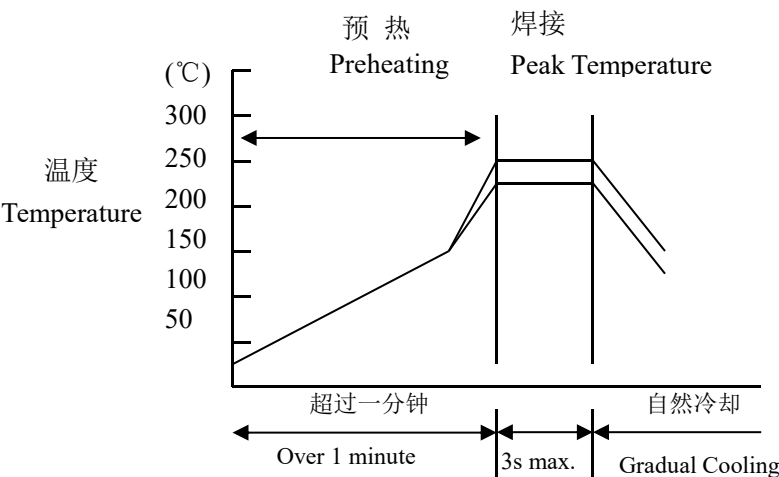

/	Pb-Sn 焊接 Pb-Sn soldering	无铅焊接 Lead-free soldering
尖峰温度 Peak temperature	230℃～260℃	240℃～270℃

在预热时，请将焊接温度与芯片表面温度之间的温差维持在 $T \leq 150^{\circ}\text{C}$ 。

While in preheating, please keep the temperature difference between soldering temperature and surface temperature of chips as: $T \leq 150^{\circ}\text{C}$.